

SO(5) theory of insulating vortex cores in high- T_c materials

Brian Møller Andersen, Henrik Bruus and Per Hedegård
*Ørsted Laboratory, Niels Bohr Institute for APG,
 Universitetsparken 5, DK-2100 Copenhagen Ø Denmark
 (June 12, 1999)*

We study the fermionic states of the antiferromagnetically ordered vortex cores predicted to exist in the superconducting phase of the newly proposed SO(5) model of strongly correlated electrons. Our model calculation gives a natural explanation of the recent STM measurements on BSCCO, which in surprising contrast to YBCO revealed completely insulating vortex cores.

PACS numbers: 74.20.De, 74.25.Ha, 74.60.-w

The SO(5) model is being developed as a candidate theory for the high- T_c superconductors. In the seminal paper by Zhang¹ the emphasis was on the phase diagram and the collective (bosonic) modes of the system. The first experimental support or in some sense the motivation for the model was the explanation of the 41 meV magnetic resonance in the superconducting state of YBCO observed by Mook *et al.*² Later the energetics of the normal-superconductivity transition was shown to explain experimental data on the condensation energy.³ More recently the foundation of the SO(5) model has been clarified by work of Rabello *et al.*⁴, Henley⁵, and Eder *et al.*⁶ These basic considerations provided the foundation for studying the Fermi-sector of the SO(5) model, and confirmed the well known electronic spectrum of the antiferromagnetic (AF) and the d -wave superconducting (dSC) phases. However, the fermionic sector has not been treated in detail, and the transport properties in the normal state still remains unresolved.

In this paper we expand on these ideas by studying the fermionic sector of the SO(5) model in the superconducting phase in the presence of Abrikosov vortices induced by an external magnetic field. It has been suggested by Arovas *et al.*⁷ that in the SO(5) model the vortex cores can become insulating, in fact antiferromagnetic, in stark contrast to the standard normal metal cores of traditional superconductors. This remarkable prediction can be tested experimentally by using the improved STM technique to directly measure the local electronic density of states in Abrikosov vortices.⁸ The metal cores predicted by Caroli *et al.*⁹ have been seen both in standard s -wave superconductors⁸ (sSC) and in the high- T_c dSC YBCO.¹⁰ The experimental advances naturally led to intensified theoretical studies of SC vortices. Following initial calculations on sSC vortex cores,^{11,12} the focus soon turned to dSC cores,¹³⁻¹⁶ and it was concluded that they are indeed metallic with states very close to the Fermi energy. Therefore, it was a surprise when Renner *et al.* observed that the vortex cores of the high- T_c superconductor BSCCO was completely devoid of low-lying electronic excitations.¹⁷ In this paper we will offer an explanation of this puzzling experimental observation by solving for the fermionic sector of the SO(5) model with insulating AF vortex cores.

In our model calculation we consider strongly correlated electrons hopping on a 2D square lattice with a lattice constant of unit length. The non-interacting Hamiltonian, H_0 , is given by an isotropic tight-binding model:

$$H_0 = -t \sum_{\mathbf{r}\sigma} \sum_{j=1}^4 c_{\sigma}^{\dagger}(\mathbf{r} + \boldsymbol{\delta}_j) c_{\sigma}(\mathbf{r}) e^{-i\frac{\pi}{4} \int_{\mathbf{r}}^{\mathbf{r}+\boldsymbol{\delta}_j} \mathbf{A} \cdot d\mathbf{l}} - \mu \hat{N} \quad (1)$$

where $\boldsymbol{\delta}_j = \{\delta_j^x, \delta_j^y\} = \{\cos[\pi(j-1)/2], \sin[\pi(j-1)/2]\}$ points to the four nearest neighbors, and where $c_{\sigma}(\mathbf{r})$ annihilates an electron with spin σ on site $\mathbf{r}$. For the interactions the spinor formalism⁴ makes it particularly simple to construct a SO(5) invariant Hamiltonian. In real space it is natural to consider the spinor

$$\Psi^{\dagger}(\mathbf{r}) = \{c_{\uparrow}^{\dagger}(\mathbf{r}), c_{\downarrow}^{\dagger}(\mathbf{r}), d_{\uparrow}(\mathbf{r}), d_{\downarrow}(\mathbf{r})\}. \quad (2)$$

The $d_{\sigma}(\mathbf{r})$ operators are associated with the sites on the opposite sublattice of the one to which $\mathbf{r}$ belongs:

$$d_{\sigma}(\mathbf{r}) = e^{-i\mathbf{Q} \cdot \mathbf{r}} \sum_{\mathbf{R}} \varphi(\mathbf{R}) c_{\sigma}(\mathbf{r} + \mathbf{R}), \quad (3)$$

where $\mathbf{Q} = (\pi, \pi)$, and where $\varphi(\mathbf{R})$ is given by

$$\varphi(\mathbf{R}) = \sum_{\mathbf{k}} e^{i\mathbf{k} \cdot \mathbf{R}} \text{sign}(\cos k_x - \cos k_y) = \frac{2}{\pi^2} \frac{1 - e^{i\mathbf{Q} \cdot \mathbf{R}}}{R_x^2 - R_y^2}, \quad (4)$$

which is only non-zero on the sublattice not including the origin. The long range nature of $\varphi(\mathbf{R})$ is crucial for the existence of strict SO(5) symmetry. $\Psi(\mathbf{r})$ transforms like a spinor under SO(5) transformations, *i.e.* under rotations in the ab plane generated by the operators $L_{ab} = \frac{1}{8} \sum_{\mathbf{r}} \Psi^{\dagger}(\mathbf{r}) \Gamma^{ab} \Psi(\mathbf{r})$, $a, b = 1, 2, 3, 4, 5$, where $\Gamma^{ab} \equiv -i[\Gamma^a, \Gamma^b]$. The five 4×4 Γ^a -matrices are given in terms of tensor products of the standard 2×2 Pauli matrices: $\Gamma^1 = \sigma_y \otimes \sigma_y$, $\Gamma^x = \mathbf{I} \otimes \sigma_x$, $\Gamma^y = \sigma_z \otimes \sigma_y$, $\Gamma^z = \mathbf{I} \otimes \sigma_z$, and $\Gamma^5 = \sigma_x \otimes \sigma_y$. The indices 2, 3, and 4 are written as x , y , and z referring to the real space directions of the AF order parameter. It can be shown⁴ that L_{15} corresponds to the charge counting operator Q , that L_{yz} , L_{zx} , and L_{xy} correspond to the spin operators S_x , S_y , and S_z , and that $L_{1(x,y,z)}$ are related to the $\pi_{(x,y,z)}$ -operators rotating between the dSC and AF sectors. As

in Ref. 4 we now focus on the vector interaction, which in the real space representation takes the form

$$H_{\text{int}} = \sum_{\mathbf{r}, \mathbf{s}} V(\mathbf{r} - \mathbf{s}) \{ \Psi^\dagger(\mathbf{r}) \Gamma^a \Psi(\mathbf{r}) \} \{ \Psi^\dagger(\mathbf{s}) \Gamma^a \Psi(\mathbf{s}) \}. \quad (5)$$

In reality the SO(5) symmetry is broken. However, both the interpretation of the 41 meV excitation as a pseudo Goldstone mode relating to a rotation of the dSC phase into the AF phase, as well as the fact that the coupling strengths in the dSC and AF sectors are almost identical,¹⁸ makes it plausible that the SO(5) breaking is weak. A natural way to break the SO(5) is simply to truncate the long range correlations apparent in Eqs. (3) and (4) for the d -operators,

$$d_\sigma(\mathbf{r}) \longrightarrow \tilde{d}_\sigma(\mathbf{r}) = \frac{1}{2} e^{-i\mathbf{Q} \cdot \mathbf{r}} \sum_{j=1}^4 \varphi_j c_\sigma(\mathbf{r} + \boldsymbol{\delta}_j), \quad (6)$$

where $\varphi_j = (-1)^{\delta_j^y}$. Maintaining only nearest neighbors in the d -operator sum constitutes a simple form relating both to SO(5) symmetry and to Hubbard-like models for dSC¹⁴. Now follow three approximations. First, we use the truncated $\tilde{d}$ -operators instead of the d -operators in the interaction Hamiltonian Eq. (5). Second, we assume a point interaction, $V(\mathbf{r} - \mathbf{s}) = -\frac{1}{8} V \delta(\mathbf{r} - \mathbf{s})$. And third, we utilize the standard mean-field approximation. These approximations result in the following SO(5) symmetry broken mean-field interaction Hamiltonian:

$$H_{\text{int}}^{\text{mf}} = - \sum_{\mathbf{r}} V [\mathbf{m}(\mathbf{r}) \cdot \langle \mathbf{m}(\mathbf{r}) \rangle + 2 \{ \Delta(\mathbf{r}) \langle \Delta^\dagger(\mathbf{r}) \rangle + \text{h.c.} \}] \quad (7)$$

with the dSC and AF order parameters given by

$$\Delta(\mathbf{r}) = \sum_{j=1}^4 \frac{\varphi_j}{4} \{ c_\uparrow(\mathbf{r} + \boldsymbol{\delta}_j) c_\downarrow(\mathbf{r}) - c_\downarrow(\mathbf{r} + \boldsymbol{\delta}_j) c_\uparrow(\mathbf{r}) \}. \quad (8)$$

$$\mathbf{m}(\mathbf{r}) = \frac{1}{2} e^{i\mathbf{Q} \cdot \mathbf{r}} \left[\begin{pmatrix} c_\uparrow^\dagger(\mathbf{r}), c_\downarrow^\dagger(\mathbf{r}) \end{pmatrix} \boldsymbol{\sigma} \begin{pmatrix} c_\uparrow(\mathbf{r}) \\ c_\downarrow(\mathbf{r}) \end{pmatrix} - \begin{pmatrix} \tilde{d}_\uparrow^\dagger(\mathbf{r}), \tilde{d}_\downarrow^\dagger(\mathbf{r}) \end{pmatrix} \boldsymbol{\sigma} \begin{pmatrix} \tilde{d}_\uparrow(\mathbf{r}) \\ \tilde{d}_\downarrow(\mathbf{r}) \end{pmatrix} \right], \quad (9)$$

We find that in $H_{\text{int}}^{\text{mf}}$ of Eq. (7) the SO(5) symmetry is broken in such a way that a d -wave gap function results in the pure SC phase, $E_{\mathbf{k}}^2 = \varepsilon_{\mathbf{k}}^2 + [2V|\Delta|(\cos k_x - \cos k_y)]^2$, while a full gap develops in the pure AF phase, $E_{\mathbf{k}}^2 = \varepsilon_{\mathbf{k}}^2 + [\frac{1}{2}Vm(1 + (\cos k_x - \cos k_y)^2)]^2$.

To elucidate the role of the gap in the AF sector we first study the continuum limit of our model. The important low-lying excitations in the fermionic sector are concentrated in the regions near the four d -wave gap nodes $\mathbf{Q}_\lambda = \frac{\pi}{2}(\cos[\pi(\lambda/2 - 1/4)], \sin[\pi(\lambda/2 - 1/4)])$, where $\lambda = 1, 2, 3, 4$. We get rid of the rapid variations by local gauge transformations in each of the four quadrants λ in $\mathbf{k}$ -space: $c_\sigma(\mathbf{r}) = \sum_\lambda e^{i\mathbf{Q}_\lambda \cdot \mathbf{r}} \psi_{\lambda, \sigma}(\mathbf{r})$. The gauge transformation is then used on H_0 (with $\mathbf{A} = 0$) and $H_{\text{int}}^{\text{mf}}$. Upon summing over $\mathbf{r}$ we keep only slowly varying terms, *i.e.* terms where $\exp[i(\mathbf{Q}_{\lambda'} \pm \mathbf{Q}_\lambda) \cdot \mathbf{r}]$ vanish. Not surprisingly, the only surviving terms are either diagonal in λ or have $\mathbf{Q}_{\lambda'} = \mathbf{Q}_\lambda + \mathbf{Q} \equiv \bar{\lambda}$. This means that $\psi_{1\sigma}(\mathbf{r})$ and $\psi_{3\sigma}(\mathbf{r}) = \psi_{\bar{1}\sigma}(\mathbf{r})$ form one subspace, and $\psi_{2\sigma}(\mathbf{r})$ and $\psi_{4\sigma}(\mathbf{r}) = \psi_{\bar{2}\sigma}(\mathbf{r})$ form the other. Thus it becomes natural to consider the spinors $\Psi_\lambda^\dagger(\mathbf{r}) = \{ \psi_{\lambda\uparrow}^\dagger(\mathbf{r}), \psi_{\bar{\lambda}\downarrow}^\dagger(\mathbf{r}), \psi_{\lambda\downarrow}^\dagger(\mathbf{r}), \psi_{\bar{\lambda}\uparrow}^\dagger(\mathbf{r}) \}$. The gauge factor $e^{i\mathbf{Q}_\lambda \cdot \mathbf{r}}$ leads to a sign change between the terms $\psi_{\lambda\sigma}(\mathbf{r} + \boldsymbol{\delta}_j)$ and $\psi_{\lambda\sigma}(\mathbf{r} - \boldsymbol{\delta}_j)$ in H_0 and Δ . The difference terms arising from this becomes derivatives in the continuum limit. Further care is necessary regarding extra $\mathbf{Q}_\lambda$ -dependent signs. For simplicity we assume $\mathbf{m}(\mathbf{r}) = m(\mathbf{r})\mathbf{e}_z$ and obtain a final Hamiltonian for the Ψ_1 spinor ($\lambda = 1$ and $\bar{\lambda} = 3$) containing both $\Delta(\mathbf{r})$ and $m(\mathbf{r})$:

$$H(\Psi_1) = \Psi_1^\dagger(\mathbf{r}) \begin{pmatrix} t(i\partial_x + i\partial_y) & \Delta(\mathbf{r})^*(i\partial_x - i\partial_y) & m(\mathbf{r}) & 0 \\ \Delta(\mathbf{r})(i\partial_x - i\partial_y) & -t(i\partial_x + i\partial_y) & 0 & -m(\mathbf{r}) \\ m(\mathbf{r}) & 0 & -t(k_+ - E) & -\Delta^*k_- \\ 0 & -m(\mathbf{r}) & -\Delta k_- & tk_+ - E \end{pmatrix} \Psi_1(\mathbf{r}). \quad (10)$$

With the Ansatz $\Psi_1^\dagger(\mathbf{r}) = (a_1, a_2, a_3, a_4)e^{-i\mathbf{k} \cdot \mathbf{r}}$, and $k_\pm = k_x \pm k_y$ for $\mathbf{k} = (k_x, k_y)$ the eigenvalue problem becomes

$$\begin{vmatrix} tk_+ - E & \Delta^*k_- & m & 0 \\ \Delta k_- & -tk_+ - E & 0 & -m \\ m & 0 & -tk_+ - E & -\Delta^*k_- \\ 0 & -m & -\Delta k_- & tk_+ - E \end{vmatrix} = 0, \quad (11)$$

A pure SC phase has a constant SC order parameter Δ , while $m = 0$, and the spectrum becomes $E = \pm \sqrt{t^2k_+^2 + |\Delta|^2k_-^2}$. The corresponding eigenstates are

easily found. For a pure AF phase m is a constant and $\Delta = 0$. The spectrum now becomes $E = \pm \sqrt{t^2k_+^2 + m^2}$, with associated eigenstates.

We now imagine the plane to be divided into two parts. For $x < 0$ the system is in the SC phase while for $x > 0$ it is in the AF phase. It is now simple to study the scattering problem where a particle with energy $|E| < m$ in the SC sector is moving towards the barrier formed by the AF sector. The result is not surprising: if the particle starts out with a momentum near, say, $\mathbf{Q}_\lambda$ it is reflected completely by the AF sector (where it only acquires an

exponentially damped probability), and it ends up with a momentum near either $\mathbf{Q}_\lambda$ or $\mathbf{Q}_{\bar{\lambda}}$. The process resembles Andreev reflection in the quantum number λ . The conclusion of this exactly solvable model is clear: low energy particles in the SC sector can be confined by a surrounding AF sector, or conversely, the AF sector expels low energy particles.

We now proceed to discuss dSC vortices, first briefly mentioning the case of normal cores followed by our SO(5) model calculation of vortices with AF cores. In his semiclassical analysis of the electronic density of states produced by d -wave vortices, Volovik showed¹³ that only a small part of the density of states results from quasiparticles localized at the vortex cores, and that that part is a function of the vortex density. Hence, in any realistic calculation of quasiparticle states, the entire vortex lattice must be taken into account. Wang and MacDonald¹⁴ made the first self-consistent, numerical lattice calculation of a tight-binding model for d -wave type-II superconductors using the Bogoliubov-de Gennes equations. In the following we expand their work to the case of d -wave superconductors with antiferromagnetic cores as described by the SO(5) model. We take advantage of earlier self-consistent calculations of isolated vortices in the SO(5) model,^{7,18} where in the symmetric gauge $\mathbf{A}_0(\mathbf{r}) = \frac{\hbar}{2e} \frac{\alpha_0(r)}{r} \mathbf{e}_\theta$ the SC and AF order parameters as a function of the distance to the vortex core in polar coordinates are given by $\Delta(\mathbf{r}) = f_0(r)e^{i\theta(r)}$ and $m(\mathbf{r}) = m_0(r)$, respectively. Here the functions $f_0(r)$, $\alpha_0(r)$ and $m_0(r)$ are only known numerically. Note that $\mathbf{m}(\mathbf{r})$ points in a constant direction, so only the size $m(\mathbf{r})$ is given. For a lattice of non-overlapping vortices, *i.e.* vortices further than a few times the London length apart, the self-consistent solutions for vector potential, the SC and the AF order parameter are expressed in term of the vortex centers, $\mathbf{R}_j$, as

$$\Delta(\mathbf{r}) = f(\mathbf{r})e^{i\theta(\mathbf{r})} = \prod_j f_0(\mathbf{r} - \mathbf{R}_j)e^{i\sum_k \text{Arg}(\mathbf{r} - \mathbf{R}_k)} \quad (12)$$

$$m(\mathbf{r}) = \sum_j m_0(\mathbf{r} - \mathbf{R}_j) \quad (13)$$

$$\mathbf{A}(\mathbf{r}) = \sum_j \mathbf{A}_0(\mathbf{r} - \mathbf{R}_j), \quad (14)$$

where $\text{Arg}(\mathbf{r} - \mathbf{R}_k)$ is the polar angle between $\mathbf{r}$ and $\mathbf{R}_k$. In a lattice model a particularly simple way to construct the magnetic unit cell is the following. For each area penetrated by one flux quantum h/e a Dirac anti-vortex string carrying a flux $-h/e$ is added.¹⁹ The strings will have no physical consequences at all when placed between lattice sites. However, they allow for the construction of a vector potential periodic in the magnetic unit cell, through which the magnetic flux is zero.

We now construct a square Abrikosov lattice with a Dirac anti-vortex added to the center of every second vortex. Since each vortex carry half a flux quantum, the smallest magnetic unit cell possible consists of two vor-

tices. However, due to better convergence properties in obtaining the periodic vector potential and a periodic representation of the SC order parameter (especially its phase $\theta(\mathbf{r})$), we choose to double the magnetic unit cell. Our unit cell contains two ordinary vortices on one diagonal and two vortices penetrated by Dirac anti-vortices on the other. Periodic forms of $\mathbf{A}(\mathbf{r})$, $\theta(\mathbf{r})$, and $m(\mathbf{r})$ are then easily found by adding up contributions from a large number of unit cells (typically 64) surrounding the one we are studying. From this we obtain a mean field lattice Hamiltonian $H = H_0 + H_{\text{int}}^{\text{mf}}$ given by Eqs. (1) and (7), which is periodic in our unit cell. Based on the Bogoliubov transformation for operators within our unit cell

$$(\gamma_\sigma^\alpha)^\dagger = \sum_{\mathbf{r}} \{u^\alpha(\mathbf{r})c_\sigma^\dagger(\mathbf{r}) + \sigma v^\alpha(\mathbf{r})c_{\bar{\sigma}}(\mathbf{r})\}, \quad (15)$$

where $\sigma = \pm 1$ is the spin index and $\bar{\sigma} = -\sigma$, the equation of motion for the γ_σ^α -operators using the periodic Hamiltonian H leads to the Bogoliubov-de Gennes equation for the eigenenergies and eigenstates of the fermionic quasiparticles:

$$\begin{pmatrix} T + \sigma M & D \\ D^* & -T^* + \sigma M \end{pmatrix} \begin{pmatrix} \mathbf{u}^\alpha \\ \mathbf{v}^\alpha \end{pmatrix} = E^\alpha \begin{pmatrix} \mathbf{u}^\alpha \\ \mathbf{v}^\alpha \end{pmatrix}. \quad (16)$$

Here E^α is the quasiparticle energy, $\mathbf{u}^\alpha$ and $\mathbf{v}^\alpha$ are vectors containing the values of $u^\alpha(\mathbf{r})$ and $v^\alpha(\mathbf{r})$ on each lattice site in our unit cell, while the block matrices T , D , and M are given by

$$(T)_{\mathbf{r}\mathbf{r}'} = -te^{-i\frac{\mathbf{r}}{\hbar} \cdot \mathbf{A}} \sum_{j=1}^4 \delta_{\mathbf{r}', \mathbf{r} + \delta_j} \quad (17)$$

$$(D)_{\mathbf{r}\mathbf{r}'} = \sum_{j=1}^4 \varphi_j [D(\mathbf{r}') + D(\mathbf{r})] \delta_{\mathbf{r}', \mathbf{r} + \delta_j} \quad (18)$$

$$(M)_{\mathbf{r}\mathbf{r}'} = \sum_{j,j'=1}^4 \varphi_j \varphi_{j'} M(\mathbf{r}' - \delta_j) \delta_{\mathbf{r}', \mathbf{r} + \delta_j + \delta_{j'}} - M(\mathbf{r}') \delta_{\mathbf{r}', \mathbf{r}}, \quad (19)$$

with $D(\mathbf{r}) = \frac{1}{2}V\langle\Delta(\mathbf{r})\rangle$ and $M(\mathbf{r}) = \frac{1}{2}e^{i\mathbf{Q}\cdot\mathbf{r}}V\langle m(\mathbf{r})\rangle$.

In the numerical calculation we use a $N \times N$ lattice with $N = 44$. The origin is put in the center and the four vortices in the center of each of the quadrants. The periodicity is ensured by having $H(\mathbf{r} + N\delta_1) = H(\mathbf{r} + N\delta_2) = H(\mathbf{r})$. The Bogoliubov-de Gennes equation, Eq. (16) becomes a $2N^2 \times 2N^2$ eigenvalue problem yielding for a given value of the spin variable σ the spectrum E^α and the Bogoliubov coefficients $\mathbf{u}^\alpha$ and $\mathbf{v}^\alpha$. To compare our calculations with the experimental STM measurements on vortices^{8,10,17} and with the existing calculations¹⁴ on ordinary sSC and dSC vortices we compute the temperature dependent local density of states (LDOS) according to the standard minimal model^{11,12,14}

$$N(\mathbf{r}, E) = \sum_{\alpha} [|u^{\alpha}(\mathbf{r})|^2 \{-f'(E^{\alpha} - E)\} + |v^{\alpha}(\mathbf{r})|^2 \{-f'(E^{\alpha} + E)\}], \quad (20)$$

where $f(\varepsilon) = [\exp(\varepsilon/k_B T) + 1]^{-1}$, and where we have neglected the dispersion in the magnetic Brillouin zone. The calculation yields the LDOS shown in Fig. 1. In all cases $V = 0.8t$, $k_B T = 0.1t$ and $\mu = -0.6t$, which due to the band structure leads to an asymmetric LDOS.

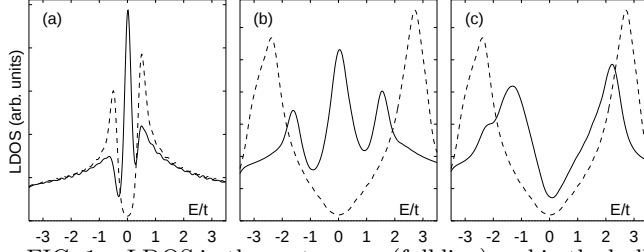


FIG. 1. LDOS in the vortex core (full line) and in the bulk SC (dashed line) for (a) BCS *s*-wave SC, (b) BCS *d*-wave SC, and (c) SO(5) SC with an AF vortex core.

First, to check our calculations, we change the model from SO(5) to ordinary sSC and dSC. The latter is produced by setting $M_{\mathbf{r},\mathbf{r}'} = 0$ in Eq. (19), and the former by furthermore setting $(D)_{\mathbf{r},\mathbf{r}'} = \frac{1}{2}V\langle\Delta(\mathbf{r})\rangle\delta_{\mathbf{r},\mathbf{r}'}$ in Eq. (18). As shown in Fig. 1a and 1b we confirm qualitatively the main conclusions of Refs. 14–16. In the bulk of the sSC phase a full gap is observed, while a mid-gap peak (which splits at $T = 0$) develops in the center of a sSC vortex. In the bulk of the dSC phase a steady rise of the LDOS is seen around the mid-gap position, while a mid-gap peak develops in the center of a dSC vortex. Our model calculation captures mainly generic features and can therefore not be used in the ongoing debate of the detailed form of the LDOS in the dSC vortex core.^{14–16} However, this issue is not important for our main observation in the SO(5) case: instead of a mid-gap peak the LDOS is dramatically suppressed in the AF vortex core resembling bulk behavior as shown in Fig. 1c. This confirms the conclusion of the dSC/AF interface in the SO(5) model studied in the first part of this paper. The AF phase effectively suppresses any fermionic low energy states.

We thus reach our main conclusion. The experimentally observed lack of electronic quasiparticle states in the center of Abrikosov vortices in BSCCO¹⁷ as opposed to the measurements of a normal metallic core of vortices in YBCO¹⁰ finds a natural explanation in the framework of the SO(5) model. As already pointed out by Arovas et al.⁷ the nature of the SO(5) vortex cores are governed by the parameters (*e.g.* doping level and coupling strengths) of the given high- T_c material. The cores can either become metallic, *i.e.* a pure dSC behavior, or insulating, *i.e.* a mixed dSC/AF behavior. At the present stage of the SO(5) theory it is difficult to predict which materials will in fact develop AF vortex cores. For example, as is studied in the striped phase²⁰, the insulating vortex cores are negatively charged, since they must be at

half filling, in contrast to the hole doped bulk material maintained at lower filling. Such a charging energy must be taken into account in a detailed calculation of the energy gained by forming an AF vortex core. Our calculation of the generic features in the fermionic sector of the SO(5) model shows that the measured LDOS can be explained if one simply assumes that YBCO with its metallic vortex cores is a pure dSC SO(5) superconductor, while BSCCO is a dSC/AF SO(5) superconductor. We obtained our results by studying both the analytically solvable model of a perfect SC/AF interface and by exact numerical diagonalization of an Abrikosov lattice model. Clearly, further theoretical insight in the dual dSC/AF nature of the high- T_c compounds can be obtained from studies of the striped phases, where alternating stripes of SC phases and AF phases occur²⁰.

This work was supported by the Danish Natural Science Research Council: access to the Cray 92 at Uni•C through Grant No. 9602481, and H.B. through Ole Rømer Grant No. 9600548.

- ¹ S.-C. Zhang, *Science*, **275**, 1089 (1997).
- ² H. A. Mook, M. Yethiraj, G. Aeppli, T. E. Mason, and T. Armstrong *Phys. Rev. Lett.* **70**, 3490 (1993).
- ³ E. Demler and S.-C. Zhang, *Nature* **396**, 733 (1998).
- ⁴ S. Rabello, H. Kohno, E. Demler, and S.-C. Zhang, *Phys. Rev. Lett.* **80**, 3586 (1998).
- ⁵ C.L. Henley, *Phys. Rev. Lett.* **80**, 3590 (1998).
- ⁶ R. Eder, W. Hanke, and S.-C. Zhang, *condmat/9707233*
- ⁷ D. Arovas, A. J. Berlinsky, C. Kallin, and S.-C. Zhang, *Phys. Rev. Lett.* **79**, 2871 (1997).
- ⁸ H.F. Hess, R.B. Robinson, R.C. Dynes, J.M. Valles, Jr., and J.V. Waszczak, *Phys. Rev. Lett.* **62**, 214 (1989); **64**, 2711 (1990).
- ⁹ C. Caroli, P.G. de Gennes, and J. Matricon, *Phys. Lett.* **9**, 307 (1964).
- ¹⁰ I. Maggio-Aprile, Ch. Renner, A. Erb, E. Walker, and Ø. Fischer, *Phys. Rev. Lett.* **75**, 2754 (1995).
- ¹¹ J.D. Shore, M. Huang, A.T. Dorsey, and J.P. Sethna, *Phys. Rev. Lett.* **62**, 3089 (1989).
- ¹² F. Gygi and M. Schlüter, *Phys. Rev. Lett.* **65**, 1820 (1990); *Phys. Rev. B* **41**, 822 (1990); **43**, 7609 (1991).
- ¹³ G.E. Volovik, *Sov. Phys. JETP* **58**, 469 (1993).
- ¹⁴ Y. Wang and A.H. MacDonald, *Phys. Rev. B* **52**, R3876 (1995).
- ¹⁵ M. Franz and Z. Tešanović, *Phys. Rev. Lett.* **80**, 4763 (1998).
- ¹⁶ K. Yasui and T. Kita, *cond-mat/9905067* (1999).
- ¹⁷ Ch. Renner, B. Revaz, J.Y. Genoud, K. Kadowaki, and Ø. Fischer, *Phys. Rev. Lett.* **80**, 149 (1998); **80**, 3606 (1998).
- ¹⁸ H. Bruus, M. Hallundbæk, and P. Hedegård, *Phys. Rev. B* **59**, 4349 (1999).
- ¹⁹ Mathematically, the Dirac string is added to a point $\mathbf{r}_0$ by the gauge transformation $\chi(\mathbf{r}) = -(\hbar/e)\text{Arg}(\mathbf{r} - \mathbf{r}_0)$.
- ²⁰ M. Veillette, Ya.B. Bazaliy, A.J. Berlinsky, C. Kallin, *cond-mat/9812282* (1998).